

PROCESSING GUIDE

WIC PP is a semi crystalline thermoplastic, reinforced with carbon fibres.


PRE-TREATMENT

Polypropylene is a non-hygroscopic polymer. Original packed granules are protected against humidity and do not require special treatment. Due to external conditions, such as climate or storage, humidity may condense on the surface of the granules and then pre-drying is recommended. Storage at ambient temperature before use will minimise condensation risk.

PROCESSING

WIC PP may be processed on all standard injection moulding machines. Wear protected plasticising units for carbon fibre reinforced compounds are advised.

In the suction conveying of carbon compounds, abrasion in the form of plastic particles, which include CF fibers, can occur. This abrasion / dust is electrically conductive due to the CF fibers. The conveying air should not escape unfiltered into the room. Special conveying air filters are to be used, which should be replaced once a week or according to susceptibility to soiling. If glass tube bends are used in the delivery piping, these are to be earthed.

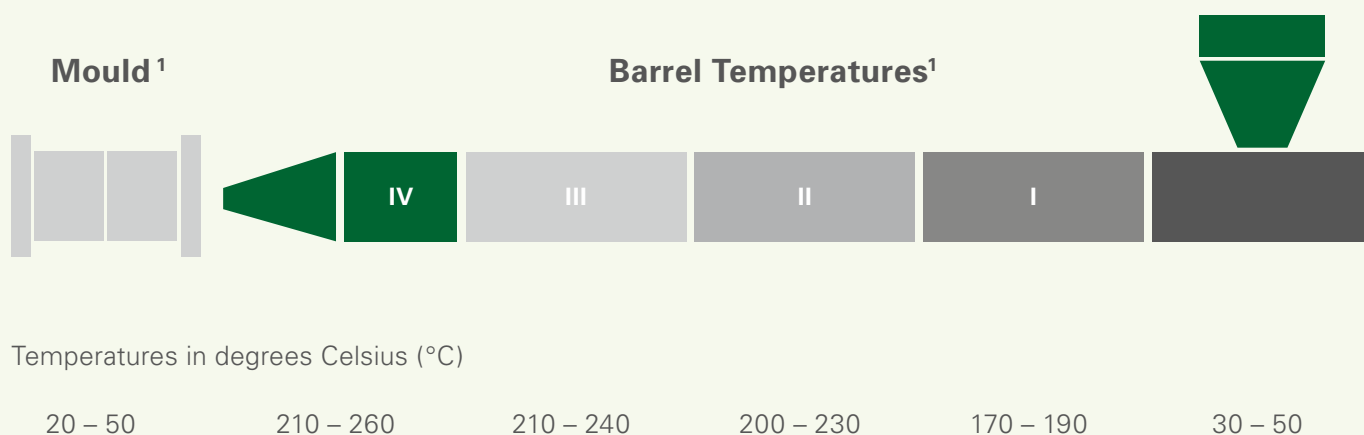

Temperatures in degrees Celsius (°C)

¹ Guide values. Standard starting profile might be in the middle.

		Unit	Notes
Properties			
Polymer abbreviation		PP	
Density (ISO 1183)	g/cm ³	0,95 – 1,11 (see Technical Data Sheet)	
Injection Machinery			
Screw stroke	Metering stroke between 1 x D and 3 x D		
Screw type	Three zone screw with L/D ratio 18:1 to 22:1		
Nozzle type	Open or shut-off possible		
Hopper type	Standard		
Pre-processing			
Storage	Dry, protected from heat and light		
Dryer type		Air circulating	Dry air
Drying time ²	h	2 – 4	2 – 3
Drying temperature ²	°C	80	
Permissible moisture content	%	< 0,15	
Processing Conditions			
Melt temperature range	°C	210 – 260	
Mould temperature range	°C	20 – 50	
Coolant	Water		
Throughput coolant	To ensure turbulent flow		
Peripheral screw speed	mm/s	< 300, e.g. screw speed of 40 rpm with a screw diameter of 50 mm	
Back pressure (specific)	bar	50 – 150	
Residence time	min	< 8	
Injection speed	Medium to fast (according to part size)		
Shrinkage³			
		Lengthwise	Crosswise
Shrinkage range (ISO 294-4)	%	0,1 – 0,5 (in mold direction)	0,1 – 0,4 (perpendicular to mold direction)

² Depends on the initial moisture content.

³ Shrinkage is influenced by the part geometry, the wall thickness of the moulding, the position and size of the gate and the processing parameters.

HEAD OFFICE

WIPAG Deutschland GmbH
 Nördliche Grünauer Straße 31
 86633 Neuburg an der Donau
 Tel.: +49 8431 4336-0
 info@wipag.de · www.wipag.de

Any information given on the chemical and physical characteristics of our products, including, without limitation, technical advice on applications, whether verbally, in writing or by testing the product, is given to the best of our knowledge and in good faith and does not exempt the buyer from carrying out their own investigations and tests in order to ascertain the product's specific suitability for the purpose intended. The buyer is solely responsible for confirming the suitability of the product for a particular application, its utilization and processing and must observe any applicable laws and government regulations.

NO EXPRESS OR IMPLIED RECOMMENDATION OR WARRANTY IS GIVEN WITH REGARD TO THE SUITABILITY OF THE PRODUCT FOR A PARTICULAR APPLICATION, SUCH AS, BUT NOT LIMITED TO, SAFETY-CRITICAL COMPONENTS OR SYSTEMS.